



Macromolecular Nanotechnology

Nanocomposites based on vapor-grown carbon nanofibers and an epoxy: Functionalization, preparation and characterization

David H. Wang^{1,2}, Sangwook Sihm^{1,2}, Ajit K. Roy¹, Jong-Beom Baek³, Loon-Seng Tan^{*1}

Nanostructured and Biological Materials Branch (AFRL/RXBN), Thermal Sciences and Management Branch (AFRL/RXBT), Materials and Manufacturing Directorate, Air Force Research Laboratory, Wright-Patterson AFB, OH 45433, USA

University of Dayton Research Institute, Dayton, OH 45469-0060, USA
Ulsan National Institute of Science and Technology, Ulsan, South Korea

ARTICLE INFO

Article history:

Received 6 January 2010

Received in revised form 23 April 2010

Accepted 27 April 2010

Available online 5 May 2010

Keywords:

Epoxy

Vapor-grown carbon nanofiber

Epoxy-functionalized

In situ nanocomposites

ABSTRACT

Vapor-grown carbon nanofibers (VGCNF) were functionalized with amine-containing pendants via a Friedel–Crafts acylation reaction with 4-(3-aminophenoxy)benzoic acid. The resulting H₂N-VGCNF was treated with epichlorohydrin, followed by sodium hydroxide solution to afford N,N-diglycidyl-modified VGCNF that is designated as epoxy-VGCNF. Subsequently, epoxy-VGCNF was dispersed in an epoxy resin (Epon 862) with the aid of acetone and sonication. After acetone had been removed under vacuum from the mixture, curing agent “W” was added to epoxy-VGCNF/Epon 862 mixture, which was then poured into molds and cured at 250 °F (121 °C) for 2 h and 350 °F (177 °C) for 2 h to form a series of epoxy/fVGCNF samples; fVGCNF designated for “functionalized VGCNF” was used to denote our belief that all epoxy functions have reacted in the resulting nanocomposites. The VGCNF content was increased from 0.10 to 10.0 wt%. For comparison purposes, the pristine VGCNF or pVGCNF (0.1–5.0 wt%) was also used in the in situ polymerization of Epon 862 and curing agent “W” to afford another series of epoxy/pVGCNF samples. The epoxy-VGCNF showed a better dispersion in the epoxy resin than pVGCNF according to SEM results. Both the tensile moduli and strengths of epoxy/fVGCNF nanocomposites are higher than those of epoxy/pVGCNF. The additive effect of VGCNF on glass-transition (*T_g*) was discussed in terms of thermal analysis results. The thermal stability of the nanocomposites was investigated by thermogravimetric analysis (TGA).

Published by Elsevier Ltd.

1. Introduction

It is well known that carbon nanotube (CNT) or carbon nanofiber (CNF) exhibits superior elastic moduli and strengths as well as high electrical and thermal conductivities, which are important for developing advanced multifunctional nanocomposites [1,2]. Therefore, they are being actively investigated with respect to their structural rein-

forcement, energy/electron transport or storage capabilities, and interactions with electromagnetic waves as well as the efficient ways to transfer their outstanding properties to the polymeric matrices. CNFs, which are more economical than CNT's (about 3–500 times cheaper than CNT), are typically produced by a vapor-phase catalytic process in which a carbon-containing feedstock (e.g. CH₄, C₂H₂, C₂H₄ etc.) is pyrolyzed in the presence of small metal catalyst (e.g. ferrocene, Fe(CO)₅ etc.) and have an outer diameter of 60–200 nm, a hollow core of 30–90 nm, and length on the order of 50–100 μm [3,4]. It follows that having aspect ratios (length/diameter) of greater than 800 should make them useful as nano-level reinforcement for polymeric matrices. Furthermore, since their inherent electrical and thermal transport properties are also excellent, there are many

* Correspondence author. Tel.: +1 (937)255 9153; fax: +1 (937)255 9157.

E-mail address: loon-seng.tan@wpafb.af.mil (L.-S. Tan).

¹ US Air Force Research Laboratory.


² University of Dayton Research Institute.

³ Ulsan National Institute of Science and Technology.

innovative possibilities for tailoring their polymer matrix composites into cost-effective, multifunctional materials. Thus, many studies related to the enhancement of the mechanical properties of an epoxy matrix by the introduction of CNF have been conducted [5–7]. Efforts to achieve homogeneous dispersion of CNFs in epoxies via chemical methods using strong acids such as sulfuric acid and nitric acid [8–10] or more elaborated schemes [11,12] have been investigated. However, strong/oxidizing acid treatment entails harsh reaction conditions, and has often brought about

structural damage to CNTs, which would dramatically decrease the conductivity and mechanical properties of CNTs.

We have developed a relatively mild method to directly arylcarbonylate vapor-grown carbon nanofibers (VGCNF) via Friedel–Crafts (F–C) acylation reaction in poly(phosphoric acid) (PPA) with aromatic carboxylic acids, and also applied the technique to graft linear and hyperbranched poly(ether-ketone)s onto pristine CNF/carbon nanotube (CNT) to generate the so-called in situ nanocomposites in a one-pot fashion [13–18]. Subsequently, in addition to

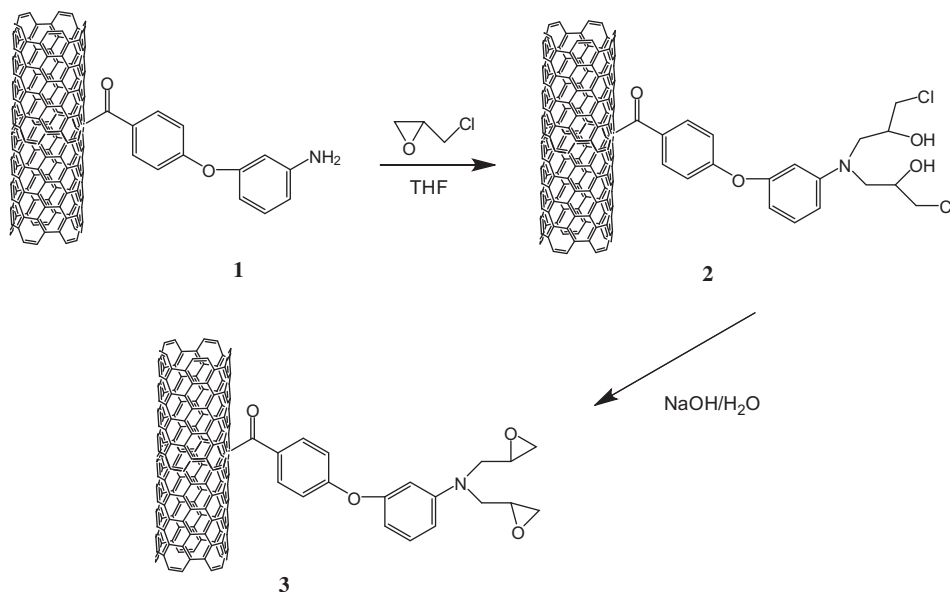

Scheme 1. Synthesis of epoxy-VGCNF (3).

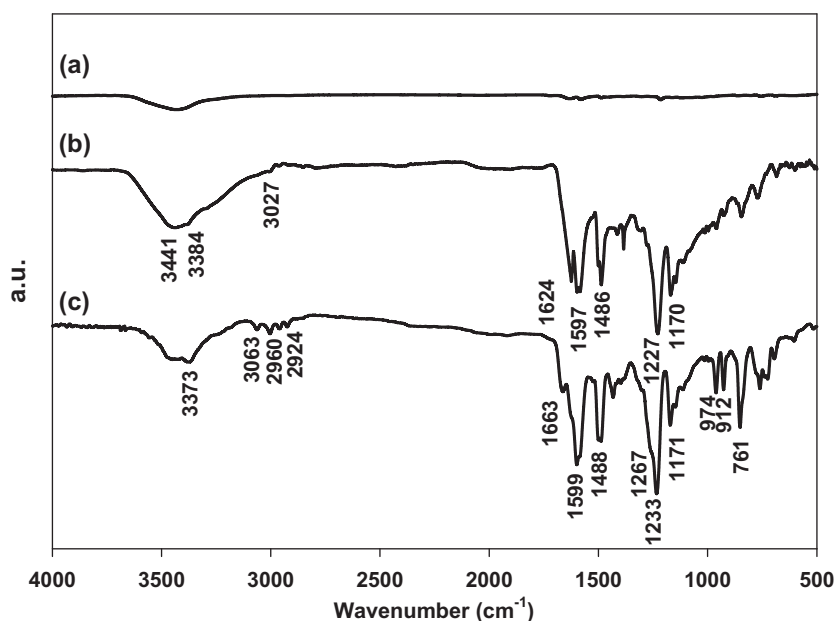


Fig. 1. FT-IR spectra of (a) pristine VGCNF, (b) NH₂-VGCNF and (c) epoxy-VGCNF.

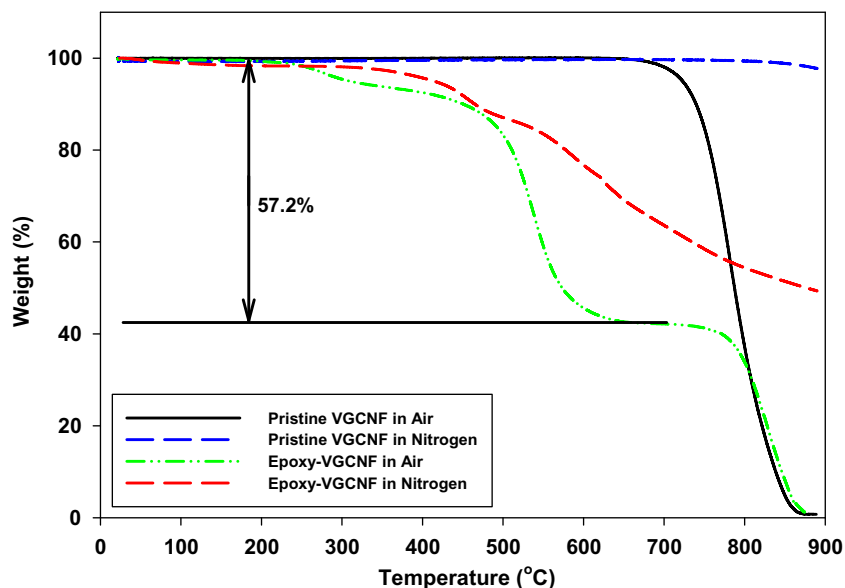


Fig. 2. TGA thermograms of pristine VGCNF and epoxy-VGCNF with heating rate of 10 °C/min.

extending the applicability of this functionalization method to MWNT, we also have found useful functionalities as part of aromatic pendants such as OH and NH₂ to be chemically unaffected in the PPA-promoted F–C acylation. Thus, when VGCNF was treated with (3-aminophenoxy)benzoic acid in PPA, NH₂-functionalized carbon nanofiber, i.e., H₂N-VGCNF, could be prepared with the degree of functionalization of ~5 atom%, and it was subsequently used to participate (co-react) in the polycondensation of 2,2-bis(phthalic anhydride)-1,1,1,3,3,3-hexafluoroisopropane (6FDA) and 1,3-bis(3-aminophenoxy)benzene (APB) to afford a series of VGCNF/polyimide nanocomposites with interesting thermal-electrical properties [19].

Glass- or carbon-fiber thermoset composites based on epoxy resins are the mainstay materials for numerous civilian and military applications. While various versions

of VGCNF with organic amine pendants have been used to serve effectively as co-curing agents and property enhancers for epoxy resins [11,20–22], it would be instructive to compare the compatibility and effectiveness of the related epoxy-functionalized CNF [23] in facilitating the processing of the nanocomposites and enhancing their properties. Thus, in this work, the aromatic amine functional group attached on the H₂N-VGCNF surface was converted in a two-step-one-pot reaction to N,N-diglycidylamino moiety. The resulting epoxy-VGCNF co-reacted in situ with epoxy monomers (Epon 862 and curing agent “W”), resulting in a series of dog-bone samples, which contained epoxy-VGCNF (corresponding to 0.10–10.0 wt% of basic VGCNF). For meaningful comparison, the pristine VGCNF (0.1–5.0 wt%) was also used in the in situ polymerization of Epon 862 and curing agent “W” to afford another series of dog-bone samples.

Table 1

Elemental analysis data for pristine and functionalized VGCNF.

Sample	Elemental analysis	C (%)	H (%)	N (%)	O (%)
Pristine	Calcd	100	0	0	0
VGCNF	Found	99.02	1.01	<0.20 ^a	<0.10 ^a
Epoxy-	Calcd ^b	82.96	3.22	2.48	11.33
VGCNF	Found	83.43	3.07	2.67	11.56

^a Less than detection limit.

^b The molecular formula of C₁₉H₁₈NO₄ is based on the assumption that for every 100 carbon there are five 4-[3-bis(3,4-diglycidyl)aminophenoxy]benzoyl groups attached, according to TGA (air) result. The molecular formula of 4-[3-bis(3,4-diglycidyl)aminophenoxy]benzoyl group are C₁₉₅H₉₀N₅O₂₀. The calculation is based on the following equation: Theoretical weight loss at 700 °C = $\frac{n \times MW_{\text{epoxy}}}{100 \times W_C + n \times MW_{\text{epoxy}}} \times 100$ where *n* is the number of 4-[3-bis(3,4-diglycidyl)aminophenoxy]benzoyl groups attached to VGCNF every 100 carbon. MW_{epoxy} is the molecular weight of 4-[3-bis(3,4-diglycidyl)aminophenoxy]benzoyl group, which is 2822.65. W_C is the atomic weight of carbon, which is 12.01. When *n* is equal to 5, theoretical weight loss at 700 °C is 57.2% based on above equation. This value is in good agreement with the weight loss at 700 °C (57.4%).

2. Experimental

2.1. Materials

Vapor-grown carbon nanofibers (VGCNF, PR-19-HT) were obtained from Applied Science Inc. (ASI), Cedarville, OH, USA via an Air Force contract. The carbon nanofibers had a typical diameter of 50–200 nm and lengths varying from 50 to 100 μm [24]. Both Epon 862 (a bis-phenol F epoxy) and “Epi-Cure” curing agent W were purchased from Miller-Stephenson Chemical Company, Inc. All other reagents and solvents were purchased from Aldrich Chemical Inc. and used as received, unless otherwise specified.

2.2. Instrumentation

Infrared (IR) spectra were recorded on a Nicolet Nexus 470 Fourier transform spectrophotometer. Elemental


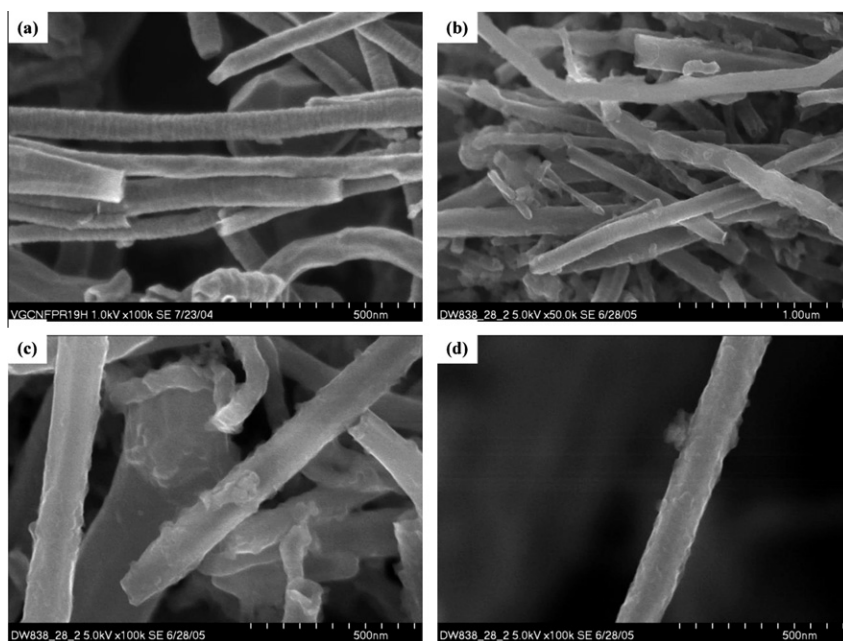


Fig. 3. SEM images of (a) as-received VGCNF ($\times 100$ k); (b) epoxy-VGCNF ($\times 50$ k); (c) epoxy-VGCNF ($\times 100$ k) and (d) epoxy-VGCNF ($\times 100$ k).

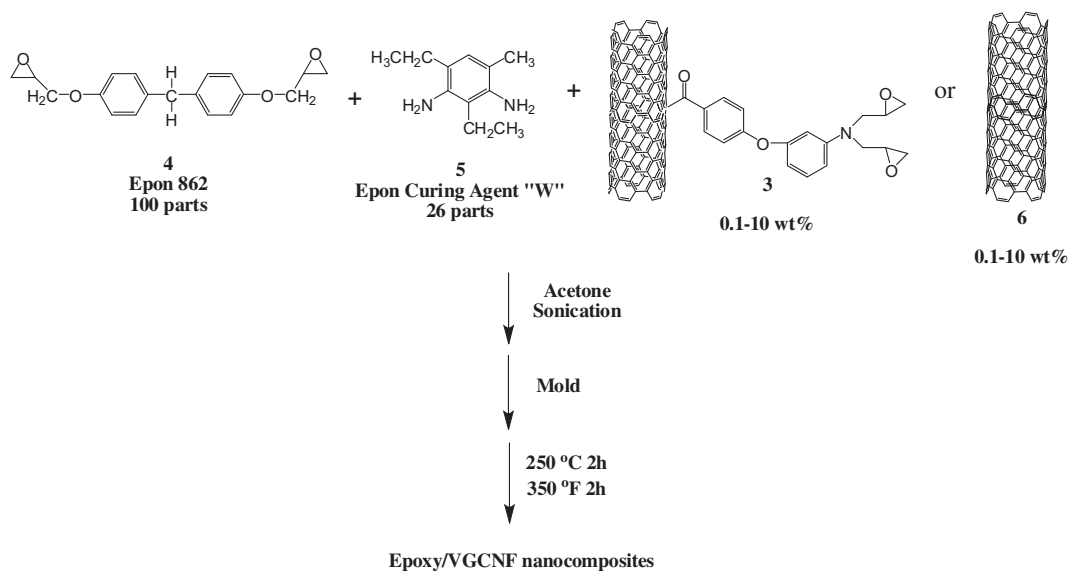

Scheme 2. Preparation of epoxy/VGCNF nanocomposites.

analysis and mass spectral analysis were performed by System Support Branch, Materials Directorate, Air Force Research Lab, Dayton, Ohio. Differential scanning calorimetry (DSC) analysis were performed in nitrogen with a heating rate of 10 °C/min using a Perkin-Elmer model 2000 thermal analyzer equipped with differential scanning calorimetry cell. Thermogravimetric analysis (TGA) was conducted in nitrogen (N₂) and air atmospheres at a heating rate of 10 °C/min using a TA Hi-Res TGA 2950 thermogravimetric analyzer. The scanning electron microscope (SEM) used in this work

was Hitachi S-520. Sonication was conducted at 20 kHz with a 600 W-power using Ace Glass GEX 600-5 Ultrasonic Processor. Tensile strength and modulus were measured using a hydraulic load frame from MTS (Model# 312.11).

2.3. Functionalization of VGCNF with 3-aminophenoxy-4-benzoic acid (1, H₂N-VGCNF)

Compound 1 was prepared according to previously reported procedure [19].

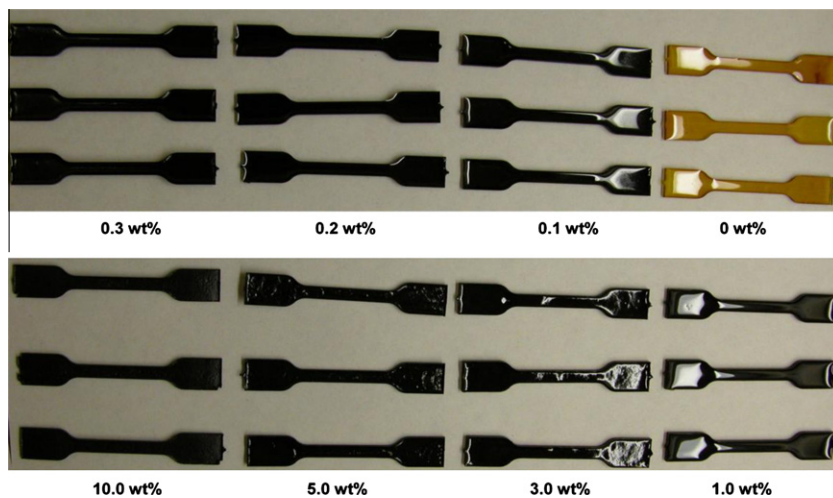


Fig. 4. Epoxy/fVGCNF dog-bone samples.

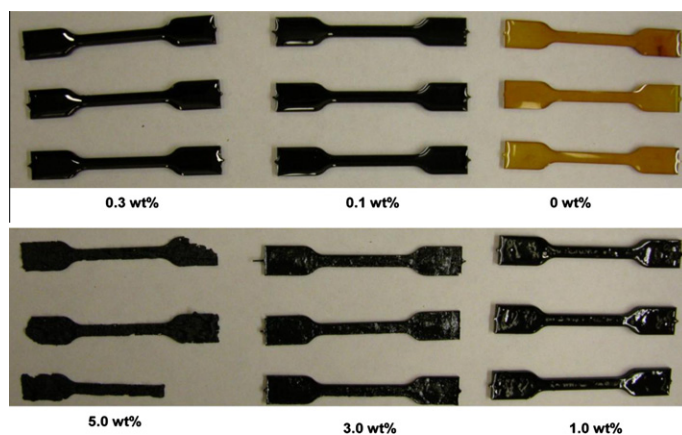


Fig. 5. Epoxy/pVGCNF dog-bone samples.

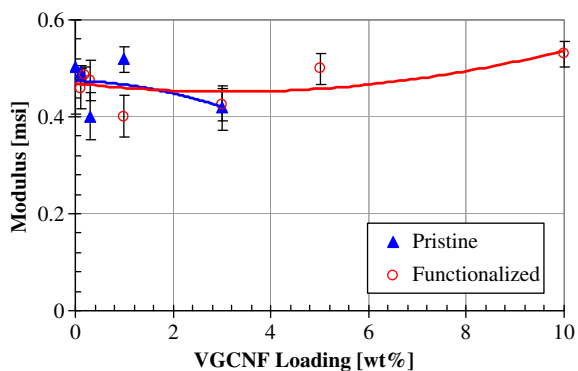


Fig. 6. Moduli of epoxy/VGCNF nanocomposites vs. VGCNF contents.

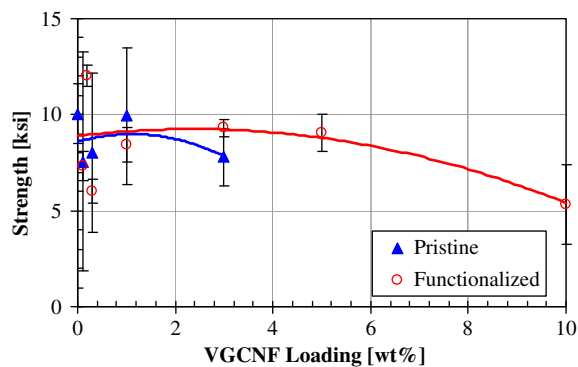


Fig. 7. Tensile strengths of epoxy/VGCNF nanocomposites vs. VGCNF contents.

2.4. Synthesis of epoxy-VGCNF (3)

Into a 250 mL three-necked, round-bottomed flask equipped with a magnetic stir-bar, nitrogen inlet, H₂N-

VGCNF (0.5 g) and THF (50 mL) were added, and the mixture was sonicated for 10 min until VGCNF was dispersed homogeneously in THF. Epichlorohydrin (5.0 g, 53.8 mmol)

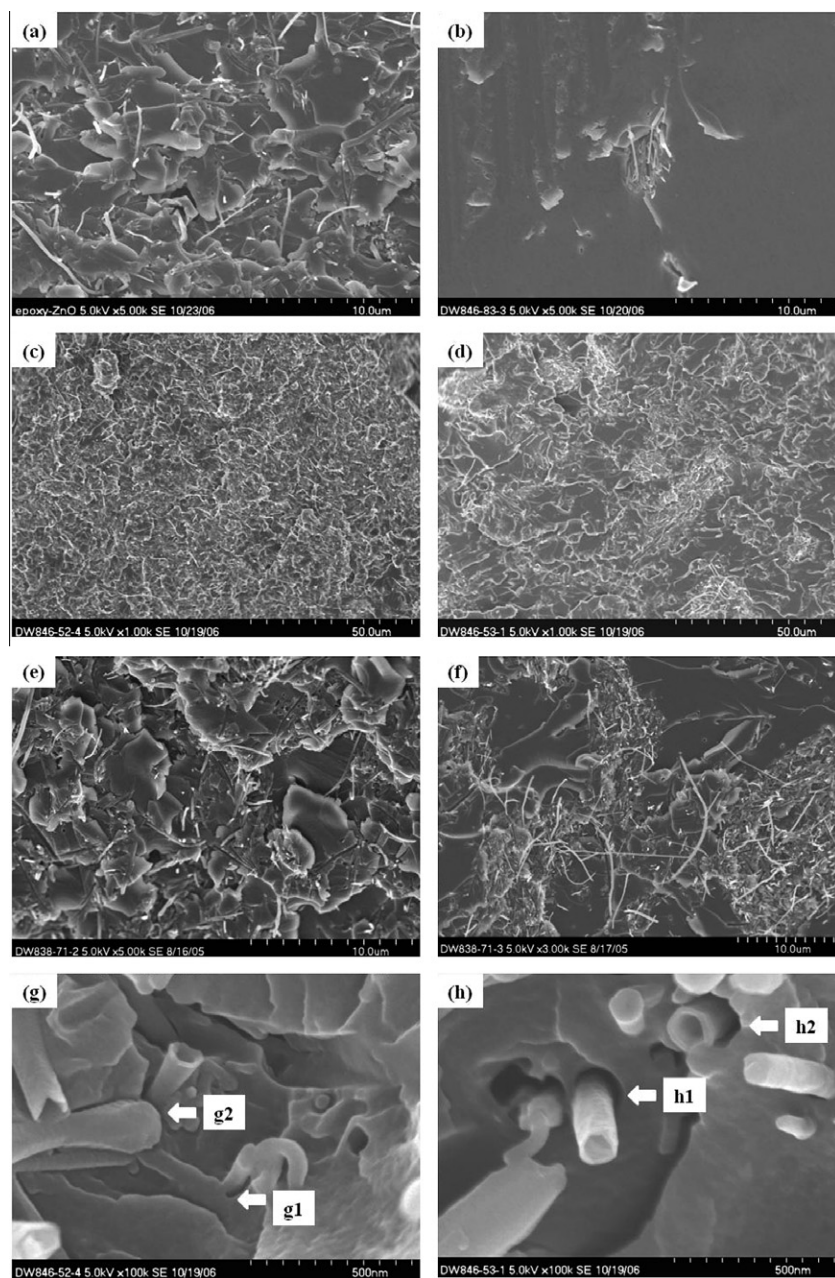


Fig. 8. SEM images of (a) 0.1 wt% epoxy/VGCNF ($\times 5$ k); (b) 0.1 wt% epoxy/pVGCNF ($\times 5$ k); (c) 5 wt% epoxy/VGCNF ($\times 1$ k); (d) 5 wt% epoxy/pVGCNF ($\times 1$ k); (e) 5 wt% epoxy/VGCNF ($\times 5$ k); (f) 5 wt% epoxy/pVGCNF ($\times 5$ k); (g) 5 wt% epoxy/VGCNF ($\times 100$ k) and (h) 5 wt% epoxy/pVGCNF nanocomposites ($\times 100$ k).

was then added. The resulting mixture was agitated and refluxed under dry nitrogen for 3 d. The reaction mixture was then allowed to cool to room temperature. Sodium hydroxide solution (50 wt%, 5.20 g, 65 mmol) was added, and the mixture was agitated under dry nitrogen at room temperature for 3 d. Finally, it was poured into water and the black precipitate was collected and washed with a large amount of water until pH reach neutral. The product was dried under vacuum at 50 °C for 24 h to afford 0.48 g (93%) of a black powder. Anal. Calcd. for $C_{195}H_{90}N_5O_{20}$: C, 82.96%; H, 3.22%; N, 2.48%. Found: C,

83.43%; H, 3.07%; N, 2.67%. FT-IR (KBr, cm^{-1}): 3373, 3063, 2960 (CH), 2924 (CH_2), 1663 (ketone carbonyl), 1599, 1488, 1233 ν_{asym} (Ar–O–Ar), 1267 ν_{sym} (epoxy; C–O–C), 1171, 974, 912 ν_{asym} (epoxy; C–O–C), 761.

2.5. Representative procedure of preparation of VGCNF/epoxy nanocomposites (epoxy resin with 5.0 wt% VGCNF load)

Epoxy-VGCNF (2.629 g) or pristine VGCNF (1.125 g) was dispersed into Epon 862 (20.0 g) by sonicating in acetone (50 mL). Acetone was removed under vacuum at room

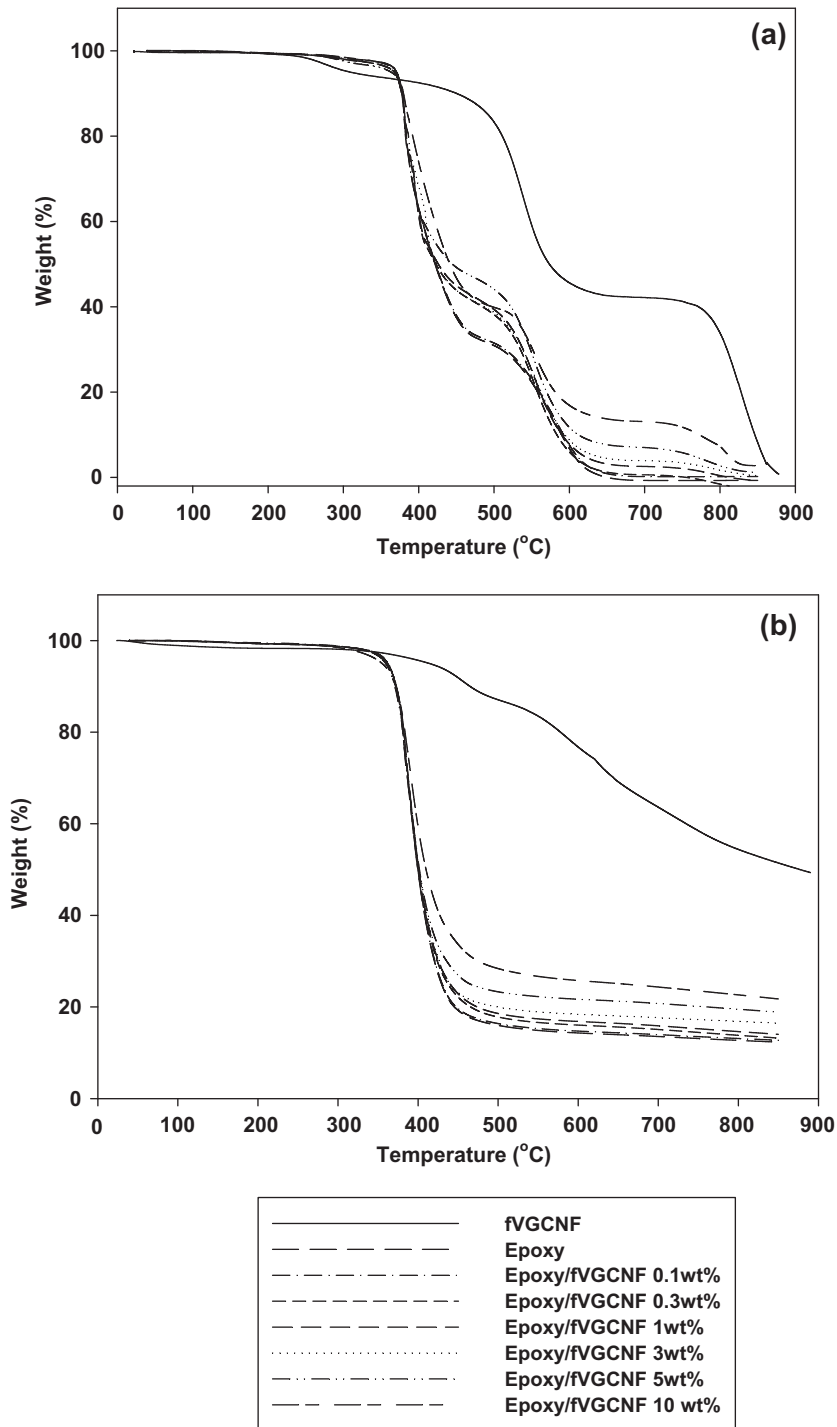


Fig. 9. TGA thermograms of epoxy/fVGCNF at heating rate of 10 °C/min (a) in air and (b) in nitrogen.

temperature. Then the curing agent “W” (5.2 g) was added. The viscous mixture was agitated for 30 min. The resulting viscous mixture was poured into dog-bone molds. The sample molds were placed into vacuum at 50 °C for 2 h to remove the bubbles formed. Finally, the dog-bone sam-

ples were heated using a 30-min temperature ramp from room temperature to 250 °F for 2 h, followed by a 30-min ramp from 250 to 350 °F for 2 h under N₂ atmosphere in an oven. They were allowed to cool to room temperature and released from silicone molds.

Table 2
Thermal properties of epoxy/fVGCNF nanocomposites.

	DSC				TGA				
	ΔH (J/g)	T_p (°C)	T_{onset} (°C)	T_g^a (°C)	In nitrogen		In air		
VGCNF (wt%)	ΔH (J/g)	T_p (°C)	T_{onset} (°C)	T_g^a (°C)	$T_{d5\%}^b$ (°C)	Char ^c (%)	$T_{d5\%}^b$ (°C)	Char ^c (%)	Char ^d (%)
100	–	–	–	–	>900	99.7	723	98.1	4.9
0 (0)	415	194	148	137	362	12.3	370	0.21	0.20
0.1 (0.23) ^e	442 (442) ^f	194	130	138	364	12.7	371	0.19	0.19
0.3 (0.69) ^e	457 (458) ^f	206	133	141	360	13.2	367	0.53	0.32
1.0 (2.33) ^e	–	–	–	134	361	14.0	368	2.53	0.78
3.0 (6.99) ^e	–	–	–	131	363	16.5	365	3.91	0.43
5.0 (11.6) ^e	471 (496) ^f	215	136	129	360	18.9	363	6.99	1.5
10.0 (23.3) ^e	–	–	–	109	355	21.7	370	13.1	2.7

^a Inflection in baseline on DSC thermogram obtained in N₂ at a heating rate of 10 °C/min.

^b Temperature at which 5% weight loss recorded on TGA thermogram obtained at a heating rate of 10 °C/min.

^c Char yield at 700 °C.

^d Char yield at 850 °C.

^e The values for the wt% based on epoxy-VGCNF are in the parenthesis.

^f Normalized values are in the parenthesis.

3. Results and discussion

3.1. Synthesis and characterization of epoxy-VGCNF

VGCNF used in this work had been thermally stripped at temperatures up to 3000 °C to graphitize any amorphous carbons. It is a complex mixture comprised of multi-walled carbon nanotubes with straight, helical, nested and bamboo configurations, of which the latter two are dominant. While the bamboo configuration is similar to that of the straight, multi-walled nanofibers, except for the presence of nodes (defect sites) along their lengths, the nested CNF, also known as fish-bone type, has an orientation similar to that of a stack of Dixie cups with a hollow core and the defect sites at the “cup rims” [25,26]. We believe that VGCNF were functionalized with amine-containing pendants at the defect sites via a Friedel–Crafts acylation reaction with 4-(3-aminophenoxy)benzoic acid to afford H₂N-VGCNF (**1**) with ca. 5 atom% functionalization [19a]. The resulting H₂N-VGCNF was subsequently treated with epichlorohydrin to form the open-chain intermediate **2**, which was directly converted to oxirane (epoxy) ring using sodium hydroxide aq. solution to afford the epoxy-containing product, epoxy-VGCNF (**3**, Scheme 1). Compound **3** exhibits the symmetrical of epoxy ring at $\sim 1270\text{ cm}^{-1}$ and asymmetrical $\nu(\text{C}-\text{O}-\text{C})$ at 912 cm^{-1} as well as the associated aliphatic C–H bands at 2959 and 2924 cm^{-1} (Fig. 1). The vibration band of carbonyl group in epoxy-VGCNF was unexpectedly shifted, but still within the range, from 1624 cm^{-1} (in H₂N-VGCNF) to 1663 cm^{-1} . The very weak band at 3373 cm^{-1} on top of the broad $\nu(\text{OH})$ band (due to difficult-to-remove water of crystallization in KBr) could be attributed to the presence of small amount of secondary amine.

The pristine VGCNF exhibited excellent thermal stability in both air and nitrogen as shown in Fig. 2. However, epoxy-VGCNF started to lose weight at 253 °C in air, and 234 °C in nitrogen, respectively, due to the decomposition of organic epoxy groups. The TGA curve taken in air showed a two-stage degradation. Epoxy-VGCNF lost 57.2% of weight between 250 and 700 °C, attributable to the loss of arylcarbonyl substituents, with 42.8% of residue

at 700 °C due to VGCNF. Based on TGA and element analysis results (Table 1 and Fig. 2), we concluded that there were approximately five arylcarbonyl groups covalently attached to the nanofiber surface for every 100 carbon sites. SEM reveals that the pristine VGCNF exhibits smooth textures such as stacked Dixie cups on the surface whereas the rough surfaces of the functionalized VGCNF are clearly indicative of modification with organic moieties (Fig. 3).

3.2. Preparation of VGCNF/epoxy nanocomposites

Epoxy-VGCNF (corresponding to 0.10–10.0 wt% of basic VGCNF composition) and the pristine VGCNF (0.1–5.0 wt%) were mixed with Epon 862 and curing agent W with the aid of both acetone and sonication. The viscous mixtures were poured into the silicone “dog-bone” molds and cured to afford a series of epoxy/epoxy-VGCNF nanocomposites (designated as epoxy/fVGCNF) and a series of epoxy/pristine VGCNF nanocomposites (designated as epoxy/pVGCNF) as shown in Scheme 2. While epoxy-VGCNF could be mixed with epoxy up to 10 wt% (Fig. 4), the maximum content of the pristine VGCNF was 3 wt%. The mixture containing 5 wt% of pristine VGCNF was too viscous to be processed. As a result, only broken dog-bone samples were obtained (Fig. 5).

3.3. Mechanical properties of epoxy/VGCNF nanocomposites

The tensile properties of two series of nanocomposites were tested and shown in Figs. 6 and 7. The tensile moduli of epoxy/fVGCNF samples are similar to the neat resin up to 5 wt%. The sample containing 10 wt% epoxy-VGCNF shows a 15% of modulus increase compared with the neat resin (0.54 msi vs. 0.47 msi). However, for the samples in which the pristine VGCNF was blended with epoxy, their moduli continue to decrease from 0.54 msi (neat resin) to 0.42 msi for 3 wt% VGCNF/epoxy samples, which corresponds about 11% lower than the modulus of neat epoxy resin cured under the same conditions. The tensile strength of the epoxy/fVGCNF composites would increase up to 6% when the VGCNF content was increased from 0 to 3 wt%.

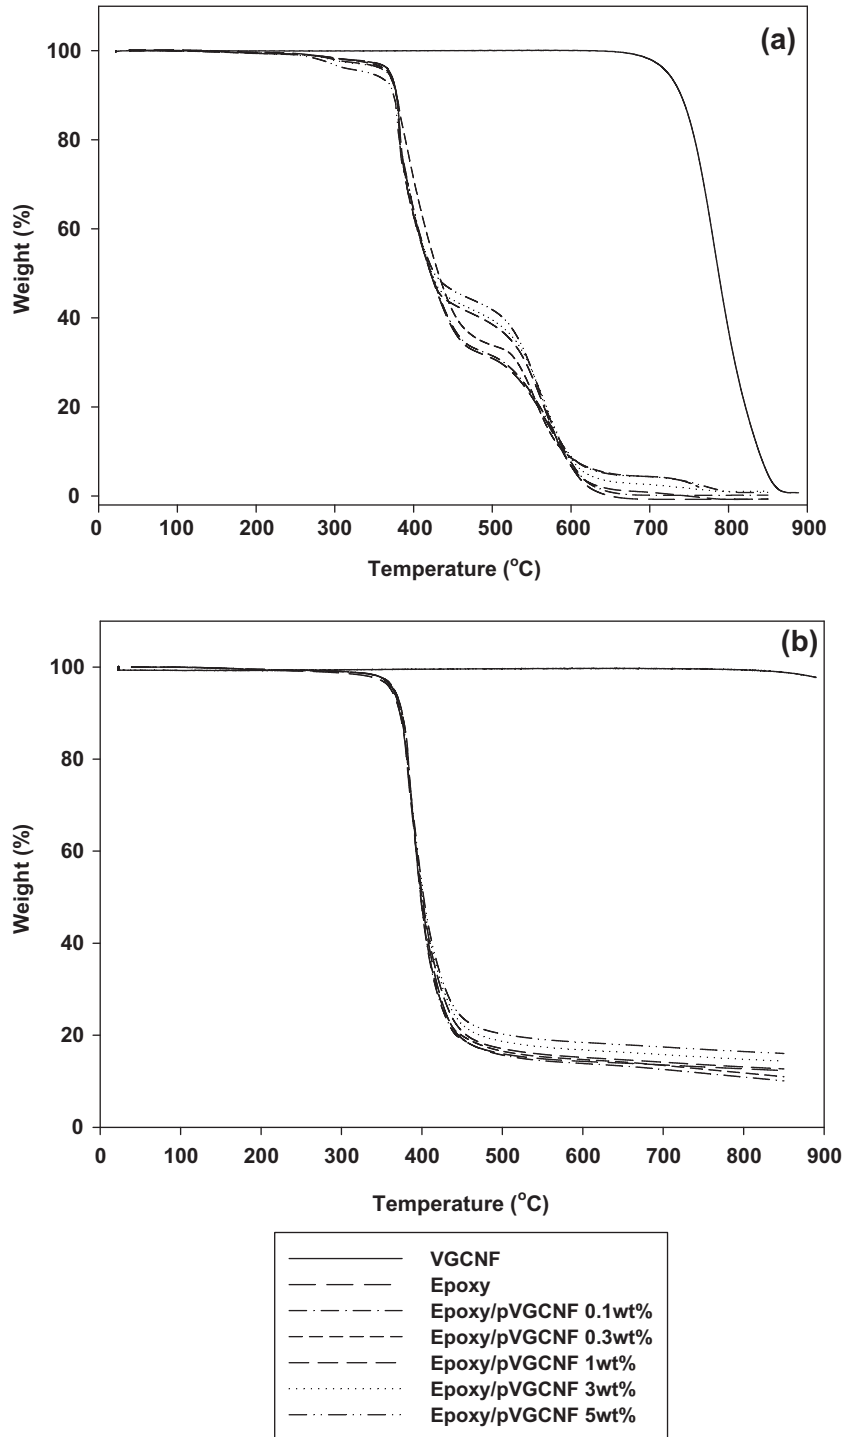


Fig. 10. TGA thermograms of epoxy/pVGCNF at heating rate of 10 °C/min (a) in air and (b) in nitrogen.

After that, the strength value would decrease as the VGCNF content was further increased to 10 wt%. The tensile strength of the pristine epoxy/pVGCNF composites would show similar trend. Albeit their strength values would only

increase to about 3% for 1 wt% epoxy/pVGCNF sample, and decrease thereafter. Therefore, the functionalized VGCNF shows better improvement of mechanical properties for epoxy than the pristine one.

Table 3
Thermal properties of epoxy/pVGCNF nanocomposites.

VGCNF (wt%)	DSC				TGA				
	ΔH (J/g)	T_p (°C)	T_{onset} (°C)	T_g^a (°C)	In nitrogen		In air		
					$T_{d5\%}^b$ (°C)	Char ^c (%)	$T_{d5\%}^b$ (°C)	Char ^c (%)	Char ^d (%)
100	–	–	–	–	>900	99.7	723	98.1	4.9
0	415	194	148	137	362	12.3	370	0.21	0.20
0.1	416 (416) ^f	194	148	142	365	10.1	371	0.33	0.19
0.3	418 (419) ^f	193	144	140	366	10.9	369	0.46	0.39
1.0	–	–	–	138	362	12.7	368	0.93	0.74
3.0	–	–	–	137	364	14.4	367	2.65	1.11
5.0	398 (419) ^f	195	145	136	365	16.0	343	4.78	2.45

^a Inflection in baseline on DSC thermogram obtained in N₂ at a heating rate of 10 °C/min.

^b Temperature at which 5% weight loss recorded on TGA thermogram obtained at a heating rate of 10 °C/min.

^c Char yield at 700 °C.

^d Char yield at 850 °C.

^f Normalized values are in the parenthesis.

3.4. Scanning Electron Microscopy (SEM)

SEM images of 0.1 and 5 wt% epoxy/fVGCNF composites show a homogenous dispersion of VGCNF in the epoxy matrix (Fig. 8a, c and e) while the 0.1 and 5 wt% epoxy/pVGCNF composites display nanofiber aggregates and phase separation between VGCNF and epoxy (Fig. 8b, d and f). Although the SEM image of epoxy/fVGCNF shows good adhesion between VGCNF and epoxy in some area, for example, in **g1** region as indicated by a white arrow in Fig. 8g due to the covalent bonding of epoxy matrix with VGCNF, in other area, the poor interfacial interaction between VGCNF and epoxy can also be seen (e.g. **g2** region). For epoxy/pVGCNF the grossly poor adhesion (i.e., appearance of detachment) between VGCNF and the epoxy matrix is evident in whole region, as shown in Fig. 8h. Therefore, the combination of better dispersion and adhesion of epoxy/fVGCNF composites probably have contributed to their higher mechanical properties than those of the epoxy/pVGCNF composites.

3.5. Thermal properties

The pristine VGCNF exhibited an expectedly high thermal stability, with 5 wt% weight loss ($T_{d5\%}$) occurring at 723 °C in air, and at temperatures higher than 900 °C in nitrogen. Epoxy/fVGCNF displayed $T_{d5\%}$ in the range of 363–370 °C in air and 355–364 °C in nitrogen, respectively (Fig. 9 and Table 2). Epoxy/pVGCNF displayed $T_{d5\%}$ in the range of 343–371 °C in air and 362–366 °C in nitrogen, respectively (Fig. 10 and Table 3). Unlike PEK/VGCNF nanocomposites, which all showed a two-stage degradation in air, both epoxy/fVGCNF and epoxy/pVGCNF samples exhibited a three-stage degradation. The aliphatic component of epoxy matrix started to degrade around 350 °C, following the decomposition onset temperature of aromatic component at 450 °C. After epoxy had been thermooxidatively stripped off, the amount of residues at 700 °C was taken as the original amount of VGCNF. Excellent agreement was obtained between the theoretical and experimental values for all the epoxy/pVGCNF compositions (Table 3). However, the experimental amounts of residues for the epoxy/fVGCNF samples at 700 °C are higher than theoretic

cal values, probably due to the carbonization of the grafted epoxy onto the VGCNF surface (Table 2).

The glass-transition (T_g) temperatures of epoxy/fVGCNF and epoxy/pVGCNF samples were determined by DSC. The samples were heated to 300 °C in the DSC chamber in the first run, and then cooled to ambient temperature at 10 °C/min under nitrogen purge. Then the samples were heated to 300 °C at 10 °C/min in the second run. The T_g 's were calculated based on mid-point of change in slope on the second heating run. In a previous work, we observed the T_g 's of *m*-polyetherketone (*m*PEK) increased gradually with VGCNF contents after *m*PEK had been grafted onto VGCNF. This is consistent with the rationale that the attachment of flexible *m*PEK chains to VGCNF had occurred [14]. In a separate work, we also observed that the T_g 's of the CP2 polyimide/VGCNF films increased at low VGCNF contents, and gradually decreased at higher VGCNF contents [19a]. In this work, we observed such similarly unusual thermal behaviors for both epoxy/fVGCNF and epoxy/pVGCNF samples. The glass transition temperature of the neat epoxy is 137 °C. The T_g values of 0.1 wt% and 0.3 wt% epoxy/fVGCNF samples were 138 and 141, an increase of 1 and 4 °C, respectively. As the VGCNF contents were incrementally increased from 0.3 to 10 wt%, the T_g 's of epoxy/fVGCNF samples would decrease from 141 to 109 °C (Table 2 and Fig. 11a). The T_g trend of epoxy/pVGCNF samples was similar to that of epoxy/fVGCNF. The T_g of 0.1 wt% epoxy/pVGCNF sample increases from 137 °C (neat epoxy) to 142 °C. Then, the T_g decreased to 140 °C for 0.3 wt% epoxy/pVGCNF sample, and further decrease to 136 °C as VGCNF contents increase to 5 wt% (Table 3 and Fig. 11b). While the T_g increase in both series of the nanocomposites at low VGCNF content could be attributed to the reinforcement effect of VGCNF on the polymer chains, it is unclear as to the reasons for the significantly and consistently lower T_g values of the epoxy/fVGCNF nanocomposites at higher VGCNF content ($\sim >1$ wt%).

As we suspect that VGCNF might have interfered with the curing process of epoxy resin at the rate that the increase of VGCNF content (especially in the case of epoxy-VGCNF) through adsorption of epoxy monomers and especially amine curing agent, which resulted in lower cross-link density and uneven distribution of cross-linked sites in the

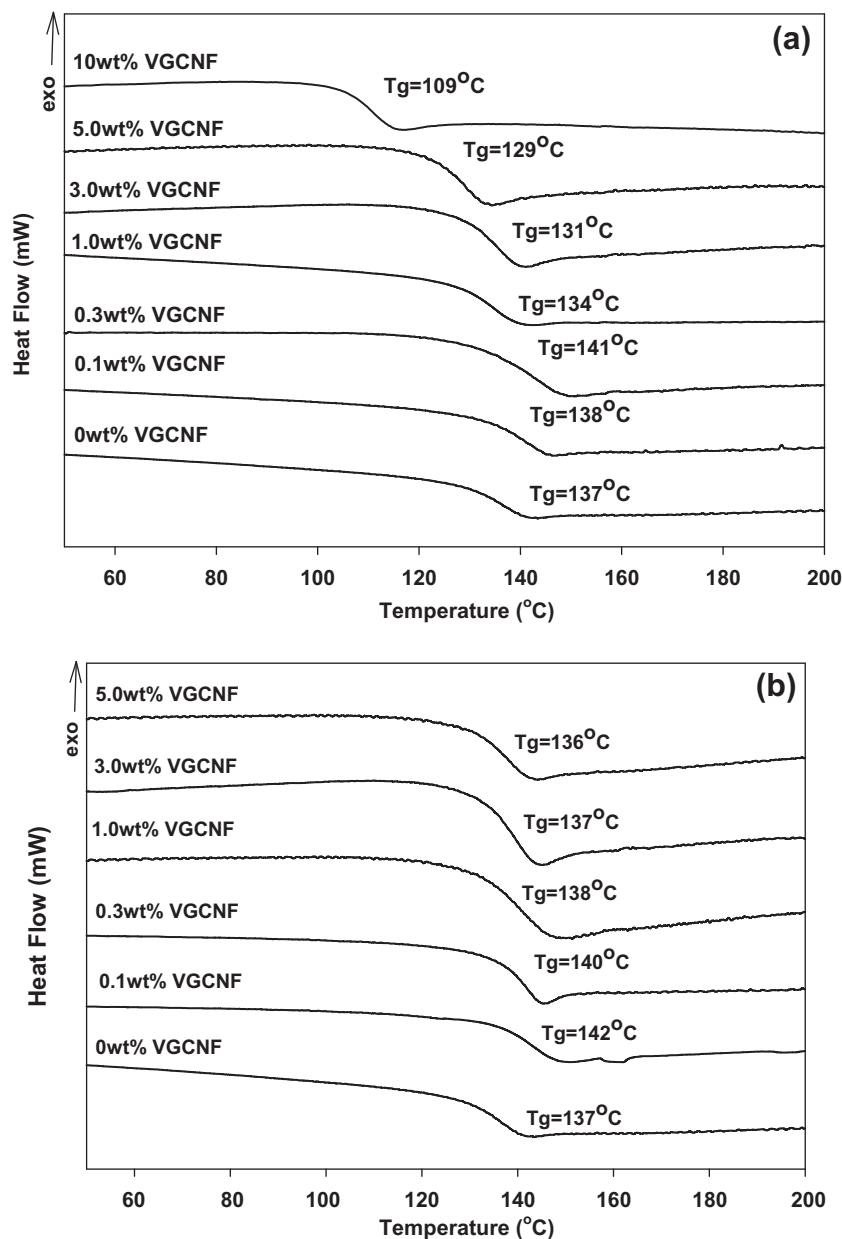


Fig. 11. DSC thermograms of (a) epoxy/VGCNF and (b) epoxy/pVGCNF with heating rate of 10 °C/min.

epoxy matrix. Therefore, the curing process of the epoxy monomers containing 0, 0.1, 0.3 and 5 wt% of epoxy-VGCNF and pristine VGCNF, respectively, were monitored using DSC (Fig. 12). Compared with neat epoxy monomers during curing process, addition of 0.1 wt% epoxy-VGCNF did not change the peak temperature of exotherm (194 °C). However, its exothermal peak is broader than that of neat epoxy resin. Upon further increase in epoxy-VGCNF content from 0.3 to 5 wt%, the curing exothermal peaks not only became broader, but their peak temperatures also increased from 194 (neat epoxy) to 215 °C (Fig. 12a and Table 2). It seems at low content (0.1 wt%) epoxy-VGCNF had minimal effect on the curing temperatures. At higher content, epoxy-

VGCNF delayed the curing process, which probably resulted in uneven distribution of crosslinking sites. The onset temperature of the neat epoxy is 148 °C. After epoxy-VGCNF was added into epoxy their onset temperatures decrease to between 130 and 136 °C. The exotherms of epoxy/VGCNF are higher than the neat resin and increase with the nanofiber contents. We speculate that crosslinking densities must be much higher in the vicinity of carbon nanofibers and less abundant. Thus, the low T_g values detected by DSC are associated with epoxy network further away from the carbon nanofibers, with lower crosslinking densities and more abundant. On the other hand, the pristine VGCNF show no effect on the exothermal peaks for 0.1, 0.3 and 5 wt%

epoxy/pVGCNF composites. While the exotherm of 0.1 wt% epoxy/pVGCNF composite is almost identical to the neat epoxy the exotherms of 0.3 and 5 wt% epoxy/pVGCNF composite are slightly broader than the neat epoxy (Fig. 12b and Table 3). The curing temperatures, onset temperatures and exotherms of epoxy/pVGCNF samples changes much less than the epoxy/fVGCNF samples, which may attribute their less T_g 's decrease than the epoxy/fVGCNF samples at higher VGCNF contents.

4. Conclusion

VGCNF was functionalized with epoxy groups on the surface via the reaction of a previously attached aromatic amine (~5 atom%) and epichlorohydrin and IR results confirmed high degree of conversion. Either the epoxy-functionalized or pristine VGCNFs was first premixed with an epoxy resin in various compositions, and then the molded mixtures was subject to the thermal curing to give two

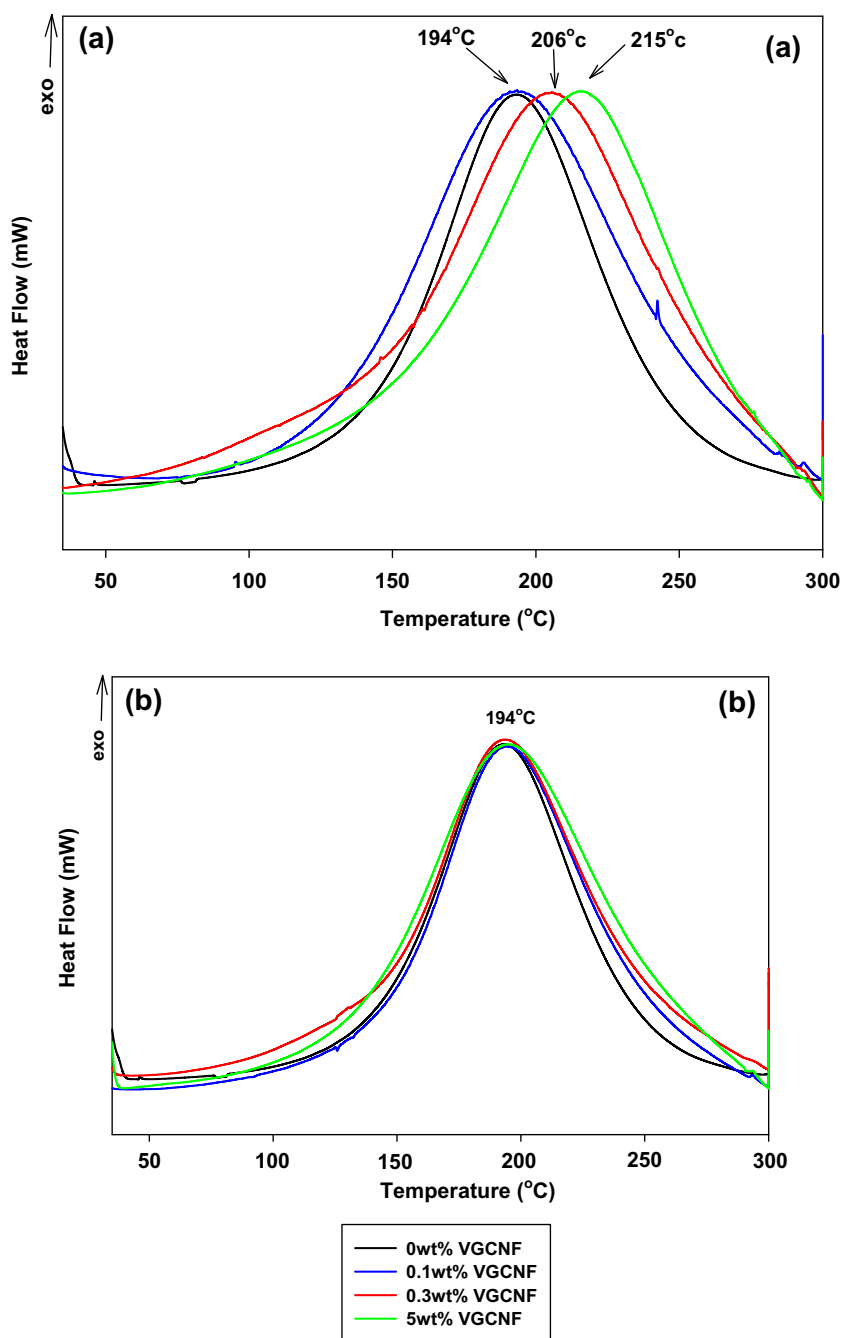


Fig. 12. DSC thermograms of (a) epoxy/fVGCNF and (b) epoxy/pVGCNF with heating rate of 10 °C/min during curing process.

series of epoxy/VGCNF nanocomposites. Higher amounts of epoxy-VGCNF (up to 10 wt%) were able to be mixed with epoxy matrix than the pristine VGCNF (3 wt%) since Epoxy-VGCNF was more compatible with epoxy. Both the tensile moduli and strengths of epoxy/fVGCNF nanocomposites are higher than those containing pristine VGCNF, due to their better dispersion in epoxy. Their thermal properties were studied using TGA and DSC. It is noteworthy that the T_g 's of both series of the nanocomposites initially increased at lower VGCNF contents, and then decreased at higher contents with more drastic decrease (up to 28 °C) for 10 wt% epoxy/fVGCNF sample. A DSC curing study indicated that the curing process of the epoxy resin in the nanocomposites was changed due to the presence (>1 wt%) of either pristine VGCNF or epoxy-functionalized VGCNF. The presence of latter apparently had an adverse effect on the glass-transition, which could be stemming from its higher affinity for the curing agent W and leading to low crosslinking densities in the bulk region away from the carbon nanotubes.

Acknowledgements

We thank Marlene Houtz, Gary Price, Sirina Putthanarat and Ronald Esterline from University of Dayton Research Institute for acquiring TGA, mechanical data and SEM images, respectively. Funding support was provided by Wright Brother Institute and Air Force Office of Scientific Research.

References

- Mahar B, Laslau C, Yip R, Sun Y. Development of carbon nanotube-based sensors. *IEEE Sens J* 2007;7:266–84.
- Mordkovich VZ. Carbon nanofibers: a new ultra-high-strength material for chemical technology. *Theor Found Chem Eng* 2003;37:429–38.
- Carneiro OS, Covas JA, Bernardo CA, Caldeira G, Hattum FWJV, Ting JM, et al. Production and assessment of polycarbonate composites reinforced with vapor-grown carbon fibers. *Compos Sci Technol* 1998;58:401–7.
- Singh C, Quested T, Boothroyd CB, Thomas P, Kinloch IA, Abou-Kandil AI, et al. Synthesis and characterization of carbon nanofibers produced by the floating catalyst method. *J Phys Chem B* 2002;106:10915–22.
- Miyagawa H, Rich MJ, Drzal LT. Thermo-physical properties of epoxy nanocomposites reinforced by carbon nanotubes and vapor grown carbon fibers. *Thermochim Acta* 2006;442:67–73.
- Kotaki M, Wang K, Toh ML, Chen L, Wong SY, He C. Electrically conductive epoxy/clay/vapor grown carbon fiber hybrids. *Macromolecules* 2006;39:908–11.
- Allaoui A, Hoa SV, Pugh MD. The electronic transport properties and microstructure of carbon nanofiber/epoxy composites. *Compos Sci Technol* 2008;68:410–6.
- Green, KJ, Dean, DR, Vaidya, UK, Nyairo, E. Multiscale fiber reinforced composites based on a carbon nanofiber/epoxy nanophased polymer matrix: synthesis, mechanical, and thermomechanical behavior. *Compos Part A* 2009;1470–5.
- Prolongo SG, Burón M, Gude MR, Chaos-Morán R, Campo M, Ureña A. Effects of dispersion techniques of carbon nanofibers on the thermo-physical properties of epoxy nanocomposites. *Compos Sci Technol* 2008;68:2722–30.
- Lafdi K, Fox W, Matzek M, Yildiz E. Effect of carbon nanofiber-matrix adhesion on polymeric nanocomposite properties-Part II. *J Nanomater* 2008 [Article ID 310126].
- Ahn S-N, Lee H-J, Kim B-J, Tan L-S, Baek J-B. Epoxy/amine-functionalized short-length vapor-grown carbon nanofiber composites. *J Polym Sci Part A: Polym Chem* 2008;46:7473–82.
- Seyhan AT, Sun Z, Deitzel J, Tanoglu M, Heider D. Cure kinetics of vapor grown carbon nanofiber (VGCNF) modified epoxy resin suspensions and fracture toughness of their resulting nanocomposites. *Mater Chem Phys* 2009;118:234–42.
- Baek J-B, Lyons CB, Tan L-S. Covalent modification of vapour-grown carbon nanofibers via direct Friedel-Crafts acylation in polyphosphoric acid. *J Mater Chem* 2004;14:2052–6.
- Baek J-B, Lyons CB, Tan L-S. Grafting of vapor-grown carbon nanofibers via in-situ polycondensation of 3-phenoxybenzoic acid in poly(phosphoric acid). *Macromolecules* 2004;37:8278–85.
- Baek J-B, Park SY, Price GE, Lyons CB, Tan L-S. Unusual thermal relaxation of viscosity-and-shear-induced strain in poly(etherketones) synthesized in highly viscous polyphosphoric acid/ P_2O_5 medium. *Polymer* 2005;46:1543–52.
- Lee H-J, Oh S-J, Choi J-Y, Kim JW, Han J, Tan L-S, et al. In situ synthesis of poly(ethylene terephthalate) (PET) in ethylene glycol containing terephthalic acid and functionalized multiwalled carbon nanotubes (MWNTs) as an approach to MWNT/PET nanocomposites. *Chem Mater* 2005;17:5057–64.
- Oh S-J, Lee H-J, Keum D-K, Lee S-W, Wang DH, Park S-Y, et al. Multiwalled carbon nanotubes and nanofibers grafted with polyetherketones in mild and viscous polymeric acid. *Polymer* 2006;47:1132–40.
- Wang DH, Baek J-B, Tan L-S. Solubilization of carbon nanofibers with a covalently attached hyperbranched poly(ether ketone). *Chem Mater* 2008;20:1502–15(a) Wang, DH, Baek, J-B, Tan, L-S. *Mater Sci Eng B* 2006;132:103.
- (a) Wang DH, Arlen MJ, Baek J-B, Vaia RA, Tan L-S. Nanocomposites derived from a low-color aromatic polyimide (CP2) and amine-functionalized vapor-grown carbon nanofibers: in situ polymerization and characterization. *Macromolecules* 2007;40:6100–11; (b) Arlen MJ, Wang DH, Tan L-S, Vaia RA. Thermal-electrical character of in situ synthesized polyimide-grafted carbon nanofiber composites. *Macromolecules* 2008;41:8053–62; (c) Trionfi A, Wang DH, Jacobs JD, Tan LS, Vaia RA, Hsu JWP. *Phys Rev* 2009;102:116601.
- Zhamu A, Hou Y, Zhong W-H, Stone JJ, Li J, Lukehart CM. Properties of a reactive-graphitic-carbon-nanofibers-reinforced epoxy. *Polym Compos* 2007;28:605–11.
- Prolongo SG, Campo M, Gude MR, Chaos-Moran R, Urena A. Thermo-physical characterisation of epoxy resin reinforced by amino-functionalized carbon nanofibers. *Compos Sci Technol* 2009;69:349–57.
- Liu W, Rice B, Klosterman D. Development and analysis of epoxy-functionalized carbon nanofibers. *SAMPE Conf Proc* 2008;53:335/1–335/16.
- Seyhan AT, Sun Z, Deitzel J, Tanoglu M, Heider D. This is the only example of epoxy-containing VGCNF that we are aware of. It is part of an aliphatic pendant as opposed to our epoxy-VGCNF, which is part of an aromatic pendant. Cure kinetics of vapor grown carbon nanofiber (VGCNF) modified epoxy resin suspensions and fracture toughness of their resulting nanocomposites. *Mater Chem Phys* 2009;118:234–42.
- Applied Sciences, Inc. Cederville, OH, USA. <<http://www.apsci.com>>.
- Lafdi K, Fox W, Matzek M, Yildiz E. Effect of carbon nanofiber heat treatment on physical properties of polymeric nanocomposite – Part I. *J Nanomater* 2007;6p [Article ID 52729].
- Toebes, ML, Bitter, JH, Jos van Dillen, A, de Jong, KP. *Catal Today* 2002;76:33–42 [and references therein].